VANADIS® 10 SUPERCLEAN^3

High performance powder metallurgical cold work tool steel

COLD WORK | PLASTIC MOULDING | HOT WORK | HIGH PERFORMANCE STEEL

UDDEHOLM

Critical tool steel properties for

GOOD TOOL PERFORMANCE

- Correct hardness for the application
- Very high wear resistance
- Sufficient toughness to prevent premature failure due to chipping/crack formation.

High wear resistance is often associated with low toughness and vice-versa. However, for optimal tool performance both high wear resistance and toughness are essential in many cases.

Vanadis 10 is a powder metallurgical cold work tool steel offering a combination of extremely high wear resistance and good toughness.

TOOLMAKING

- Machinability
- Heat treatment
- Dimensional stability in heat treatment
- Surface treatment.

Toolmaking with highly alloyed steels means that machining and heat treatment are often more of a problem than with the lower alloyed grades. This can, of course, raise the cost of toolmaking.

Due to the very carefully balanced alloying and the powder metallurgical manufacturing route, Vanadis 10 has a similar heat treatment procedure to the steel D2. One very big advantage with Vanadis 10 is that the dimensional stability after hardening and tempering is much better than for the conventionally produced high performance cold work steels. This also means that Vanadis 10 is a tool steel which is very suitable for CVD coating.

Applications

Vanadis 10 is especially suitable for very long run tooling where abrasive wear is the dominating problem. Its very good combination of extremely high wear resistance and good toughness also make Vanadis 10 an interesting alternative in applications where tooling made of such materials as cemented carbide tends to chip or crack.

Examples:

- Blanking and forming
- Fine blanking
- Blanking of electrical sheet
- Gasket stamping
- Deep drawing
- Cold forging
- Slitting knives (paper and foil)
- Powder pressing
- Granulator knives
- Extruder screws etc.

General

Vanadis 10 is a chromium-molybdenum-vanadium alloyed steel which is characterized by:

- Extremely high abrasive wear resistance
- High compressive strength
- Very good through-hardening properties
- Good toughness
- Very good stability in hardening
- Good resistance to tempering back.

Typical analysis %	C 2,9	Si 0,5	Mn 0,5	Cr 8,0	Mo 1,5	V 9,8
Delivery condition	Soft annealed to approx. 280–310 HB					
Colour code	Green/violet					

Properties

PHYSICAL DATA

Hardened and tempered to 62 HRC.

Temperature	20°C (68°F)	200°C (390°F)	400°C (750°F)
Density kg/m^3 lbs/in^3	7 400 0,268	–	–
Modulus of elasticity N/mm^2 psi	220 000 31,9 x 10^6	210 000 30,4 x 10^6	200 000 29,0 x 10^6
Coefficient of thermal expansion per pro °C ab 20°C °F from 68°F	–	10,7 x 10^{-6} 6,0 x 10^{-6}	11,4 x 10^{-6} 6,3 x 10^{-6}
Thermal conductivity W/m • °C Btu in/(ft^2 h °F)	–	20 139	22 153
Specific heat J/kg °C Btu/lb °F	460 0,11	–	–

IMPACT STRENGTH

Approximate room temperature impact strength at different tempering temperatures. Specimen size: 7 x 10 x 55 mm (0,27" x 0,40" x 2,2") unnochted. Hardened at 1020°C (1870°F). Quenched in air. Tempered twice.

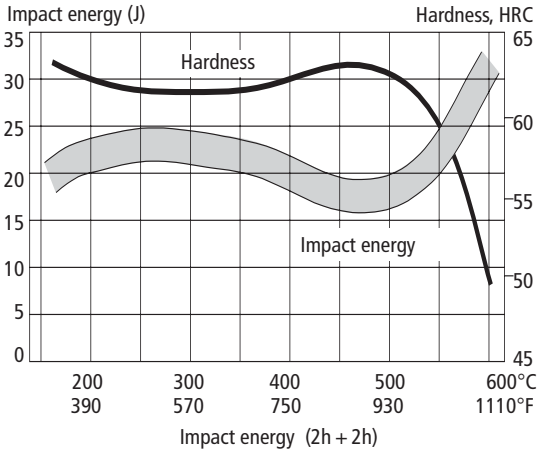

WEAR RESISTANCE

Pin on disc test. Disc material: SiC.
Vanadis 10 = 62 HRC, D2 = 62 HRC.

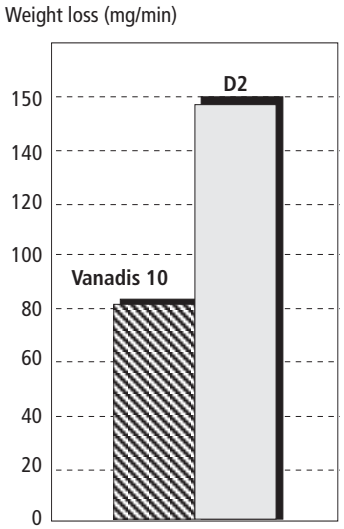

Heat treatment

SOFT ANNEALING

Protect the steel and heat through to 900°C (1650°F). Cool in the furnace at 10°C (20°F) per hour to 750°C (1380°F), then freely in air.

STRESS RELIEVING

After rough machining the tool should be heated through to 650°C (1200°F), holding time 2 hours. Cool slowly to 500°C (930°F), then freely in air.

HARDENING

Pre-heating temperature: 600–700°C (1110–1290°F)
Austenitizing temperature: 1020–1100°C (1870–2010°F)
Holding time: 30 minutes.
N.B. Holding time = time at hardening temperature after the tool is fully heated through. A holding time of less than 30 minutes will result in loss of hardness.

The tool should be protected against decarburization and oxidation during hardening.

QUENCHING MEDIA

- Forced air/gas
- Vacuum furnace (gas overpressure 2–5 bar)
- Martempering bath or fluidized bed at 500–550°C (930–1020°F)
- Martempering bath or fluidized bed at 200–350°C (390–660°F) whereby 350°C (660°F) is preferred.

Note 1: Temper the tool as soon as its temperature reaches 50–70°C (120–160°F).

Note 2: In order to obtain the optimum properties for the tool, the cooling rate should be as fast as is concomitant with acceptable distortion.

Note 3: Tools with sections >50 mm (2") should be quenched in forced air. Quenching in still air will result in loss of hardness.

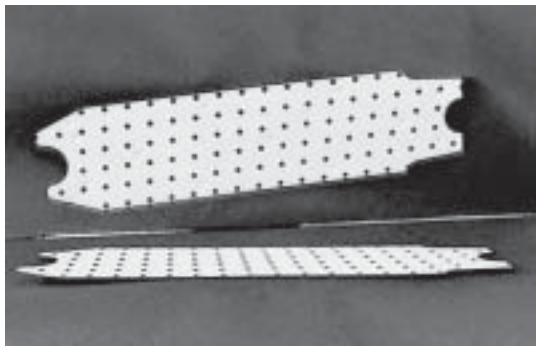

TTT-graph

Austenitizing temperature 1020°C (1870°F). Holding time 30 minutes.

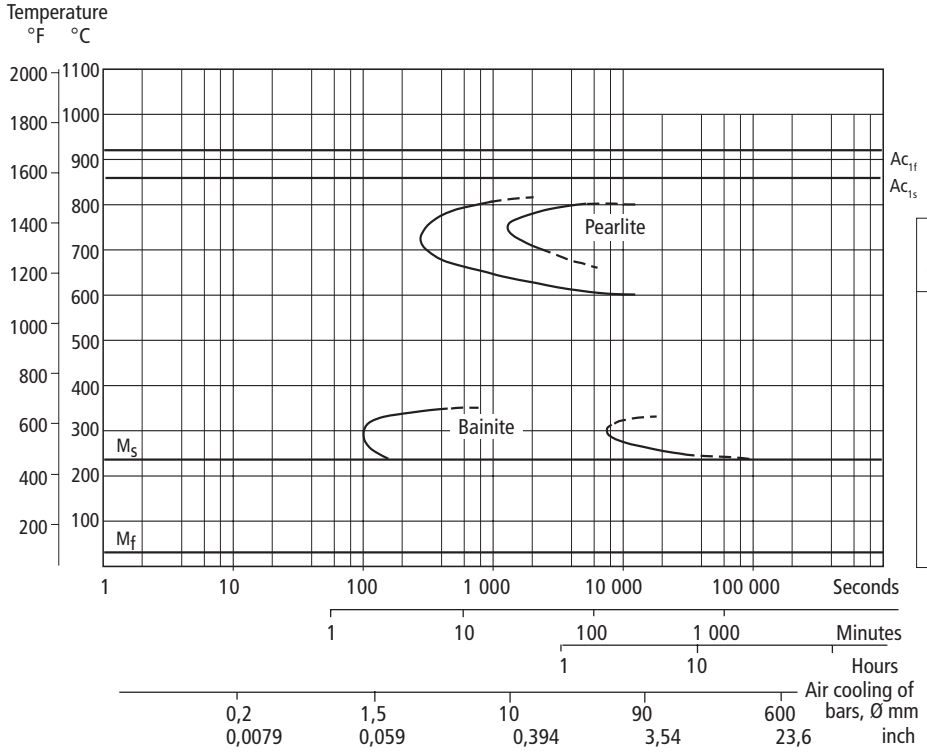

Iso-thermal Temp.°C	Time hours	Hardness HV10 (approx.)
800	4,5	297
750	18	302
700	1,1	350
675	22	354
650	4	423
600	23	523
500	44	890
425	61	890
400	22,5	890
350	15	858
325	3,5	715
300	7	642
250	22	673

CCT-graph

Austenitizing temperature 1020–1060°C (1870–1940°F). Holding time 30 minutes.

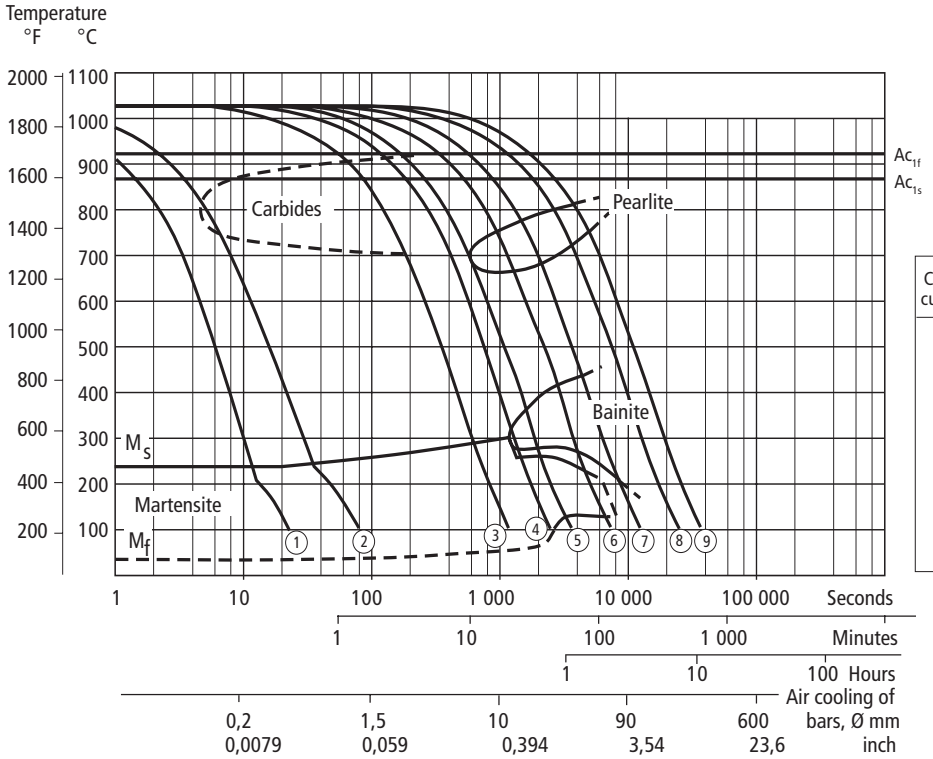

Cooling curve Nr	Hardness HV 10	$T_{800-500}$ (sec.)
1	890	3,8
2	878	10
3	818	232
4	806	481
5	731	695
6	635	1389
7	509	2318
8	325	4633
9	311	6947

Hardness and retained austenite as functions of austenitizing temperature.

Holding time 30 min. Air-cooling.

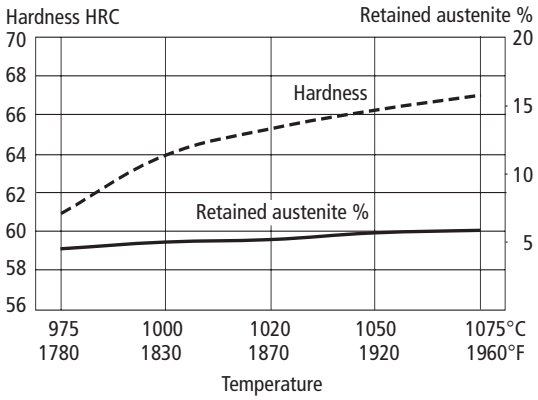

TEMPERING

Choose the tempering temperature according to the hardness required by reference to the tempering graph. Temper twice with intermediate cooling to room temperature. Lowest tempering temperature 180°C (360°F). Holding time at temperature minimum 2 hours. At a hardening temperature of 1100°C (2010°F) or higher Vanadis 10 should be tempered at minimum 525°C (980°F) in order to reduce the amount of retained austenite

Tempering graph

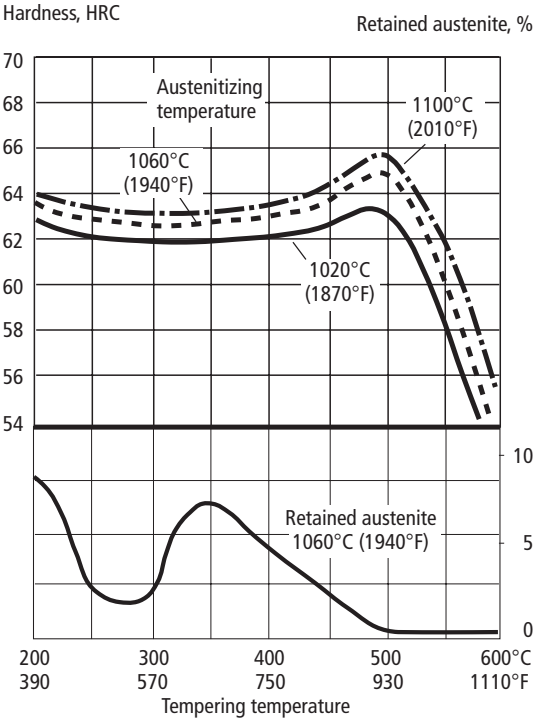

DIMENSIONAL CHANGES AFTER TEMPERING

Specimen size: 65 x 65 x 65 mm (2,5" x 2,5" x 2,5")

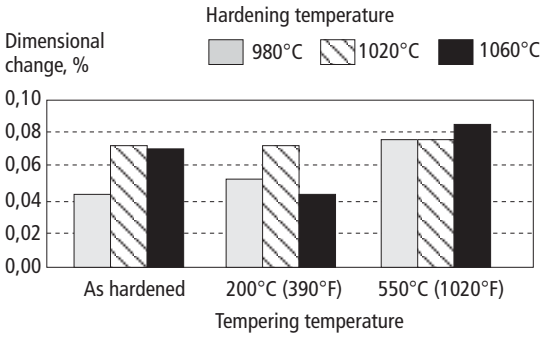

Specimen size: 125 x 125 x 25 mm (5" x 5" x 1")

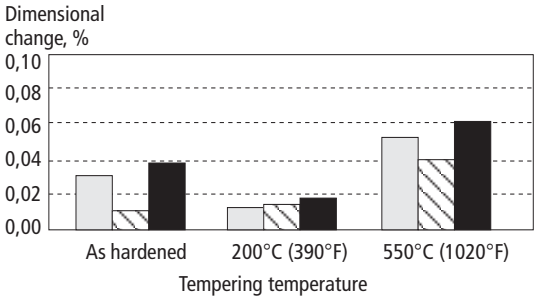

SUB-ZERO TREATMENT

Pieces requiring maximum dimensional stability can be sub-zero treated as follows:
Immediately after quenching the piece should be sub-zero treated to between –70 and –80°C (–95 to –110°F), soaking time 1–3 hours, followed by tempering.
Sub-zero treatment will give a hardness increase of ~1 HRC. Avoid intricate shapes as there will be risk of cracking.

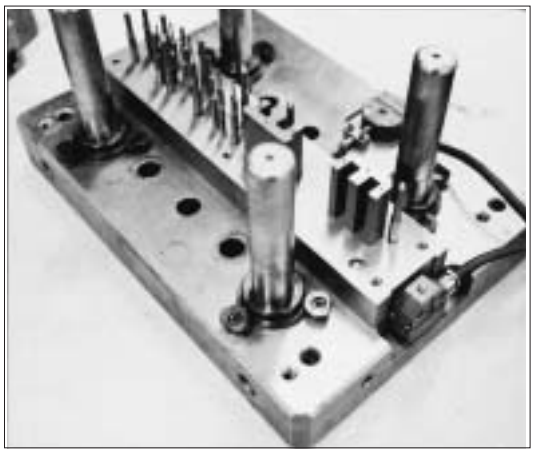

Typical application for Vanadis 10. Tool for blanking and forming eletcrical strip.

NITRIDING

Nitriding produces a hard surface layer that increases wear resistance and reduces the tendency towards galling.
If high temperature tempered Vanadis 10 is normally tempered at 525°C (980°F). This means that the nitriding temperature used should not exceed 500–525°C (930–980°F). Ion nitriding at a temperature below the tempering temperature used is preferred.
The surface hardness after nitriding is approximately 1250 $HV_{0,2\ kg}$. The thickness of the layer should be chosen to suit the application in question.

Cutting data recommendations

The cutting data below are to be considered as guiding values which must be adapted to existing local conditions.

Delivery condition: Soft annealed to 280–310 HB

TURNING

Cutting data parameter	Turning with carbide		Turning with high speed steel
	Rough turning	Fine turning	Fine turning
Cutting speed (v_c) m/min f.p.m.	50–80 160–260	80–100 260–330	5–8 16–26
Feed (f) mm/r i.p.r.	0,2–0,4 0,008–0,016	0,05–0,2 0,002–0,008	0,05–0,3 0,002–0,012
Depth of cut (a_p) mm inch	2–4 0,08–0,16	0,5–2 0,02–0,08	0,5–3 0,02–0,12
Carbide designation ISO	K20*	K15*	–

**Use a wear resistant Al_2O_3-coated carbide grade*

DRILLING

High speed steel twist drill

Drill diameter mm	Drill diameter inch	Cutting speed, vc m/min	Cutting speed, vc f.p.m.	Feed (f) mm/r	Feed (f) i.p.r.
–5	–3/16	6–8*	20–26*	0,05–0,15	0,002–0,006
5–10	3/16–3/8	6–8*	20–26*	0,15–0,20	0,006–0,008
10–15	3/8–5/8	6–8*	20–26*	0,20–0,25	0,008–0,010
15–20	5/8–3/4	6–8*	20–26*	0,25–0,35	0,010–0,014

** For coated HSS drill vc 12–14 m/min. (40–45 f.p.m.)*

Carbide drill

Cutting data parameters	Type of drill		
	Indexable insert	Solid carbide	Carbide tipped coolant-fed[1]
Cutting speed (v_c) m/min. f.p.m.	70–90 230–295	40–60 130–200	20–30 65–100
Feed (f) mm/r i.p.r.	0,05–0,15[2] 0,002–0,006	0,10–0,25[2] 0,004–0,010	0,15–0,25[2] 0,006–0,010

[1] Drill with internal cooling channels and brazed carbide tip.
[2] Depending on drill diameter.

MILLING

Face and square shoulder milling

Cutting data parameter	Milling with carbide	
	Rough milling	Fine milling
Cutting speed (v_c) m/min. f.p.m.	30–50 100–160	50–70 160–230
Feed (f_z) mm/tooth in/tooth	0,2–0,4 0,008–0,016	0,1–0,2 0,004–0,008
Depth of cut (a_p) mm inch	2–4 0,08–0,16	–2 0,08
Carbide designation ISO	K20–P20 coated carbide	K15–P15 coated carbide or cermet

End milling

Cutting data parameter	Type of mill		
	Solid carbide	Carbide indexable insert	High speed steel[1]
Cutting speed (v_c) m/min. f.p.m.	30–40 100–130	30–50 100–160	10–14 30–34
Feed (f_z) mm/tooth in/tooth	0,03–0,20[2] 0,001–0,008	0,08–0,20[2] 0,003–0,008	0,05–0,35[2] 0,002–0,05
Carbide designation ISO	–	K 15[3]	–

[1] Uncoated HSS is not recommended
[2] Depending on radial depth of cut and cutter diameter.
[3] Use a wear resistant Al_2O_3-coated carbide grade.

GRINDING

A general grinding wheel recommendation is given below. More information can be found in the Uddeholm publication "Grinding of tool steel".

Type of grinding	Annealed condition	Hardened condition
Face grinding straight wheel	A 46 HV	B151 R50 B3[1)] A 46 GV[2)]
Face grinding segments	A 36 GV	A 46 GV
Cylindrical grinding	A 60 KV	B151 R75 B3[1)] A 60 JV[2)]
Internal grinding	A 60 JV	B151 R75 B3[1)] A 60 IV
Profile grinding	A 100 IV	B126 R100 B6[1)] A 100 JV[2)]

[1)] If possible, use CBN-wheels for this application.
[2)] Preferable a wheel type containing sintered Al_2O_3 (seeded gel)

Electrical-discharge machining–EDM

If EDM is performed in the hardened and tempered condition, finish with "fine-sparking", i.e. low current, high frequency.
For optimal performance the EDM'd surface should then be ground/polished and the tool retempered at approx. 25°C (50°F) lower than the original tempering temperature.
When EDM'ing larger sizes or complicated shapes Vanadis 10 should be tempered at high temperatures, above 500°C (930°F).

Typical application area for Vanadis 10: high volume production of electrical components.

Relative comparison of Uddeholm cold work tool steel

MATERIAL PROPERTIES AND RESISTANCE TO FAILURE MECHANISMS

Uddeholm grade	Hardness/ Resistance to plastic deformation	Machinability	Grindability	Dimension stability	Resistance to: Abrasive wear	Resistance to: Adhesive wear	Fatigue cracking resistance: Ductility/ resistance to chipping	Fatigue cracking resistance: Toughness/ gross cracking
CALMAX	■	■	■	■	■	■	■	■
SLEIPNER	■	■	■	■	■	■	■	■
SVERKER 21	■	■	■	■	■	■	■	■
VANADIS 4	■	■	■	■	■	■	■	■
VANADIS 6	■	■	■	■	■	■	■	■
VANADIS 10	■	■	■	■	■	■	■	■
VANADIS 23	■	■	■	■	■	■	■	■
VANADIS 30	■	■	■	■	■	■	■	■
VANADIS 60	■	■	■	■	■	■	■	■
AISI M:2	■	■	■	■	■	■	■	■

Further information

Please contact your local Uddeholm office for further information on the selection, heat treatment, application and availability of Uddeholm tool steel.

UDDEHOLM EUROPE

AUSTRIA
UDDEHOLM
Hansaallee 321
D-40549 Düsseldorf
Telephone: +49 211 535 10
Telefax: +49 211 535 12 80

BELGIUM
UDDEHOLM N.V.
Waterstraat 4
B-9160 Lokeren
Telephone: +32 9 349 11 00
Telefax: +32 9 349 11 11

CROATIA
BOHLER UDDEHOLM Zagreb
d.o.o za trgovinu
Zitnjak b.b
10000 Zagreb
Telephone: +385 1 2459 301
Telefax: +385 1 2406 790

CZECHIA
BOHLER UDDEHOLM CZ s.r.o.
Division Uddeholm
U silnice 949
161 00 Praha 6 Ruzyne
Czech Republic
Telephone: +420 233 029 850,8
Telefax: +420 233 029 859

DENMARK
UDDEHOLM A/S
Kokmose 8, Bramdrupdam
DK-6000 Kolding
Telephone: +45 75 51 70 66
Telefax: +45 75 51 70 44

ESTONIA
UDDEHOLM TOOLING AB
Silikatsiidi 7
EE-0012 Tallinn
Telephone: +372 655 9180
Telefax: +372 655 9181

FINLAND
OY UDDEHOLM AB
Ritakuja 1, PL 57,
FIN-01741 VANTAA
Telephone: +358 9 290 490
Telefax: +358 9 2904 9249

FRANCE
UDDEHOLM S.A.
12 Rue Mercier, Z.I. de Mitry-Compans
F-77297 Mitry Mory Cedex
Telephone: +33 (0)1 60 93 80 10
Telefax: +33 (0)1 60 93 80 01

Branch office
UDDEHOLM S.A.
77bis, rue de Vesoul
La Nef aux Métiers
F-25000 Besançon
Telephone: +33 381 53 12 19
Telefax: +33 381 53 13 20

GERMANY
UDDEHOLM
Hansaallee 321
D-40549 Düsseldorf
Telephone: +49 211 535 10
Telefax: +49 211 535 12 80

Branch offices
UDDEHOLM
Falkenstraße 21
D-65812 Bad Soden/TS.
Telephone: +49 6196 659 60
Telefax: +49 6196 659 625

UDDEHOLM
Albstraße 10
D-73765 Neuhausen
Telephone: +49 715 898 65-0
Telefax: +49 715 898 65-25

GREAT BRITAIN, IRELAND
UDDEHOLM UK LIMITED
European Business Park
Taylors Lane, Oldbury
West Midlands B69 2BN
Telephone: +44 121 552 55 11
Telefax: +44 121 544 29 11

Dublin Telephone: +353 1 45 14 01

GREECE
UDDEHOLM STEEL TRADING COMPANY
20, Athinon Street
G-Piraeus 18540
Telephone: +30 2 10 41 72 109/41 29 820
Telefax: +30 2 10 41 72 767

SKLERO S.A.
Steel Trading Comp. and Hardening Shop
Frixou 11/Nikif. Ouranou
G-54627 Thessaloniki
Telephone: +30 31 51 46 77
Telefax +30 31 54 12 50

HUNGARY
UDDEHOLM TOOLING/BOK
Dunaharaszti, Jedlik Ányos út 25
H-2331 Dunaharaszti 1.Pf. 110
Telephone/Telefax: +36 24 492 690

ITALY
UDDEHOLM Italia S.p.A.
Via Palizzi, 90
I-20157 Milano
Telephone: +39 02 35 79 41
Telefax: +39 02 390 024 82

LATVIA
UDDEHOLM TOOLING AB
Deglava street 50
LV-1035 Riga
Telephone: +371 7 701 983, -981, -982
Telefax: +371 7 701 984

LITHUANIA
UDDEHOLM TOOLING AB
BE PLIENAS IR METALAI
T. Masiulio 18b
LT-3014 Kaunas
Telephone: +370 37 370613, -669
Telefax: +370 37 370300

THE NETHERLANDS
UDDEHOLM B.V.
Isolatorweg 30
NL-1014 AS Amsterdam
Telephone: +31 20 581 71 11
Telefax: +31 20 684 86 13

NORWAY
UDDEHOLM A/S
Jernkroken 18
Postboks 85, Kalbakken
N-0902 Oslo
Telephone: +47 22 91 80 00
Telefax: +47 22 91 80 01

POLAND
INTER STAL CENTRUM
Sp. z. o.o./Co. Ltd.
ul. Kolejowa 291, Dziekanów Polski
PL-05-092 Lomianki
Telephone: +48 22 429 2260
Telefax: +48 22 429 2266

PORTUGAL
F RAMADA Aços e Industrias S.A.
P.O. Box 10
P-3881 Ovar Codex
Telephone: +351 56 58 61 11
Telefax: +351 56 58 60 24

ROMANIA
BÖHLER Romania SRL
Uddeholm Branch
Str. Atomistilor Nr 14A
077125 Magurele Jud Ilfov
Telephone: +40 214 575007
Telefax: +40 214 574212

RUSSIA
UDDEHOLM TOOLING CIS
25 A Bolshoy pr PS
197198 St. Petersburg
Telephone: +7 812 233 9683
Telefax: +7 812 232 4679

SLOVAKIA
UDDEHOLM Slovakia
Nástrojové ocele, s.r.o
KRÁCINY 2
036 01 Martin
Telephone: +421 842 4 300 823
Telefax: +421 842 4 224 028

SLOVENIA
UDDEHOLM Italia S.p.A.
Via Palizzi, 90
I-20157 Milano
Telephone: +39 02 35 79 41
Telefax: +39 02 390 024 82

SPAIN
UDDEHOLM
Guifré 690-692
E-08918 Badalona, Barcelona
Telephone: +34 93 460 1227
Telefax: +34 93 460 0558

Branch office
UDDEHOLM
Barrio San Martin de Arteaga, 132
Pol.Ind. Torrelarragoiti
E-48170 Zamudio
(Bizkaia)
Telephone: +34 94 452 13 03
Telefax: +34 94 452 13 58

SWEDEN
UDDEHOLM TOOLING SVENSKA AB
Aminogatan 25
SE-431 53 Mölndal
Telephone: +46 31 67 98 50
Telefax: +46 31 27 02 94

SWITZERLAND
HERTSCH & CIE AG
General Wille Strasse 19
CH-8027 Zürich
Telephone: +41 1 208 16 66
Telefax: +41 1 201 46 15

UDDEHOLM NORTH AMERICA

USA
UDDEHOLM
4902 Tollview Drive
Rolling Meadows IL 60008
Telephone: +1 847 577 22 20
Telefax: +1 847 577 80 28

UDDEHOLM
548 Clayton Ct.,
Wood Dale IL 60191
Telephone: +1 630 350 10 00
Telefax: +1 630 350 08 80

UDDEHOLM
9331 Santa Fe Springs Road
Santa Fe Springs, CA 90670
Telephone: +1 562 946 65 03
Telefax: +1 562 946 77 21

UDDEHOLM
220 Cherry Street
Shrewbury, MA 01545
Telephone: +1 508 845 1066
Telefax: +1 508 845 3471

CANADA
UDDEHOLM LIMITED
2595 Meadowvale Blvd.
Mississauga, Ontario L5N 7Y3
Telephone: +1 905 812 9440
Telefax: +1 905 812 8659

MEXICO
ACEROS BOHLER UDDEHOLM, S.A. de C.V.
Calle 8 No 2, Letra "C"
Fraccionamiento Industrial Alce Blanco
C.P. 52787 Naucalpan de Juarez
Estado de Mexico
Telephone: +52 55 9172 0242
Telefax: +52 55 5576 6837

UDDEHOLM
Lerdo de Tejada No.542
Colonia Las Villas
66420 San Nicolas de Los Garza, N.L.
Telephone: +52 8-352 5239
Telefax: +52 8-352 5356

UDDEHOLM SOUTH AMERICA

ARGENTINA
UDDEHOLM S.A
Mozart 40
1619-Centro Industrial Garin
Garin-Prov. Buenos Aires
Telephone: +54 332 744 4440
Telefax: +54 332 745 3222

BRAZIL
UDDEHOLM ACOS ESPECIAIS Ltda.
Estrada Yae Massumoto, 353
CEP 09842-160
Sao Bernardo do Campo - SP Brazil
Telephone: +55 11 4393 4560, -4554
Telefax: +55 11 4393 4561

UDDEHOLM SOUTH AFRICA
UDDEHOLM Africa (Pty) Ltd.
P.O. Box 539
ZA-1600 Isando/Johannesburg
Telephone: +27 11-974 2781
Telefax: +27 11-392 2486

UDDEHOLM AUSTRALIA
BOHLER-UDDEHOLM Australia
129-135 McCredie Road
Guildford NSW 2161
Private Bag 14
Telephone: +61 2 9681 3100
Telefax: +61 2 9632 6161

Branch offices
Sydney, Melbourne, Adelaide, Brisbane, Perth, Newcastle, Launceston, Albury, Townsville

ASSAB

ASSAB INTERNATIONAL
Skytteholmsvägen 2
P O Box 42
SE-171 11 Solna
Sweden
Telephone: +46 8 564 616 70
Telefax: +46 8 25 02 37

Subsidiaries
India, Iran, Turkey, United Arab Emirates
Distributors in
Africa, Latin America, Middle East

ASSAB PACIFIC
ASSAB Pacific Pte. Ltd
171, Chin Swee Road
No. 07-02, San Centre
Singapore 169877
Telephone: +65 534 56 00
Telefax: +65 534 06 55

Subsidiaries
China, Hong Kong, Indonesia, Japan, Korea, Malaysia, Philippine Islands, Singapore, Taiwan, Thailand

When the first idea pops into your head, throughout the development process to the release of the new product, we'll be your partner. As the world's leading supplier of tooling materials and related services, we can be trusted. Meet us under the Uddeholm and ASSAB brands, wherever in the world you have your business.

UDDEHOLM
WWW.UDDEHOLM.COM

Edition: 4, 03.2004